



## Steel grade

Material No. / Werkstoff-Nr.	PREMIUM 1.2714
Description	55NiCrMoV7
AISI/SAE	L6; T61206
Search for alternatives in the ABRAMS STEEL GUIDE®	<a href="http://www.steel-guide.eu/alternatives/L6">www.steel-guide.eu/alternatives/L6</a>

## Specifications



€co-Präz® [€co]  
L: 500 mm



Precision round steel  
with machining allowance [PRS/BA]  
peeled / rough-turned  
L: 500 mm  
L: 1.000 mm

## Chemical composition AISI/SAE L6 (reference value %)

C	Si	Mn	P	S	Cr	Mo	Ni	V
0,5 - 0,6	0,1 - 0,4	0,6 - 0,9	0 - 0,03	0 - 0,03	0,8 - 1,2	0,35 - 0,55	1,5 - 1,8	0,05 - 0,15

## Physical properties

Hardness (delivery condition)	max. 250 HB, annealed					
Tensile strength $R_m$ (as received condition)	approx. 850 N/mm <sup>2</sup>					
Working hardness	max. 54 HRC					
Thermal expansion coefficient $10^{-6}m/(m \cdot K)$	20 - 100°C	20 - 200°C	20 - 300°C	20 - 400°C	20 - 500°C	20 - 600°C
	12,2	13,0	13,3	13,7	14,2	14,4
Thermal conductivity $W/(m \cdot K)$	20°C	350°C	700°C			
	36,0	38,0	35,0			

## Technical properties

Hot work steel that can be used for a wide range of applications. With good through-hardening, tempering resistance, toughness, pressure and heat resistance.

## Applications


Forging dies, slides, punch heads, extruding stamps, press tools, hot shear knives, extrusion press tools, die holders, support tools, tool holders, pressure plates, armoured die plates.




## Heat treatment

Soft annealing	Temperature	Cooling		Hardness					
	650 - 700°C	Furnace		max. 250 HB					
Stress relief annealing	Temperature	Cooling							
	600 - 650°C	Furnace							
Hardening	Temperature	Quenching in			Hardness after quenching				
	830 - 870°C 860 - 900°C	Oil Air			58 HRC 56 HRC				
Tempering	100°C	200°C	300°C	400°C	450°C	500°C	550°C	600°C	650°C
	Oil Air	57 HRC 55 HRC	54 HRC 52 HRC	52 HRC 50 HRC	49 HRC 47 HRC	47 HRC 45 HRC	46 HRC 43 HRC	43 HRC 40 HRC	38 HRC 36 HRC

## Thermal expansion coefficient diagram

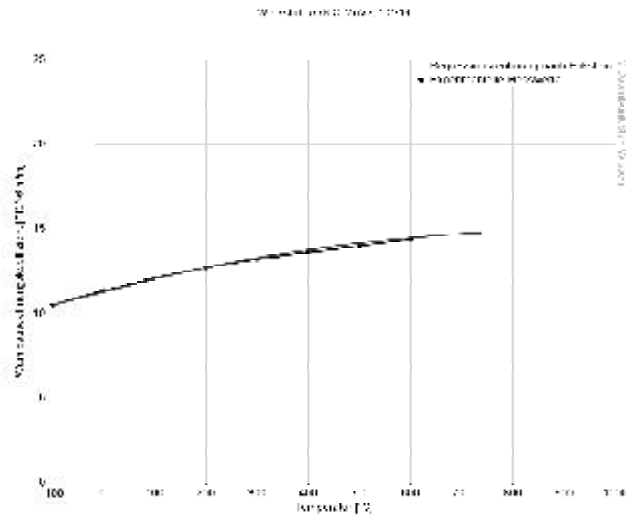

## Thermal conductivity diagram

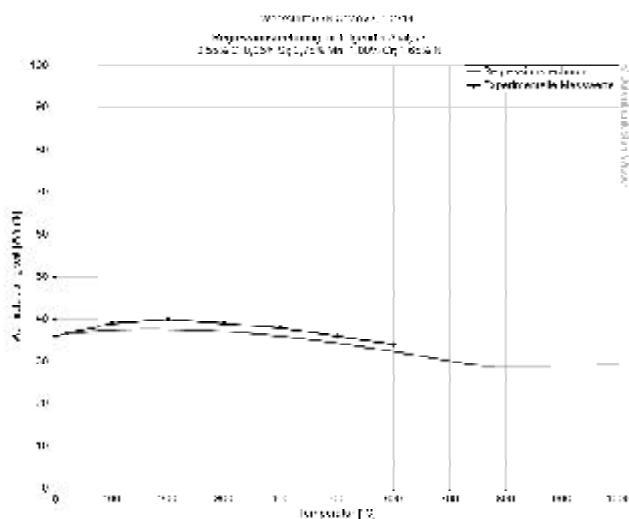

### ABRAMS PREMIUM STEEL

is a registered trademark of  
Abrams Engineering Services GmbH & Co. KG  
Hannoversche Str. 38 · 49084 Osnabrueck / Germany  
Managing Director: Dipl.-Wi.-Ing. Dr. Juergen Abrams

Amtsgericht Osnabrueck / Germany, HRA 6865  
VAT-No.: DE 221940667  
General Partner: Abrams Engineering Verwaltungs GmbH  
Amtsgericht Osnabrueck / Germany, HRB 20019


T: +49 (0) 5 41/3 57 39-0  
F: +49 (0) 5 41/3 57 39-39

sales@premium-steel.eu  
www.premium-steel.eu  
www.shop.premium-steel.eu  
www.steel-guide.eu


[www.premium-steel.eu/news](http://www.premium-steel.eu/news)




**Thermal capacity diagram**

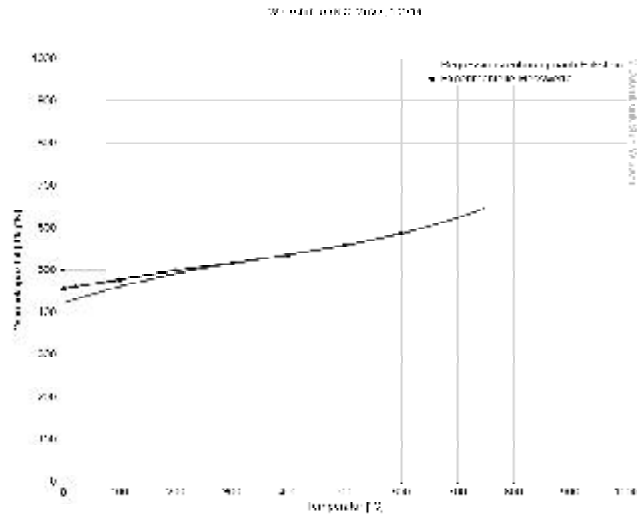


**Continuous ZTU-diagram**

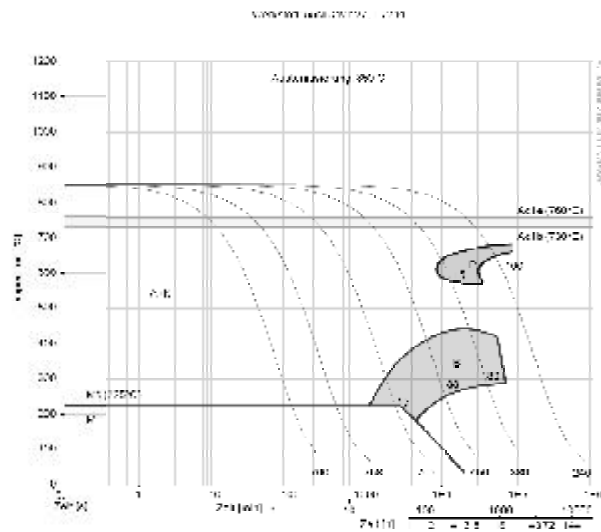


## Isothermal ZTU-diagram

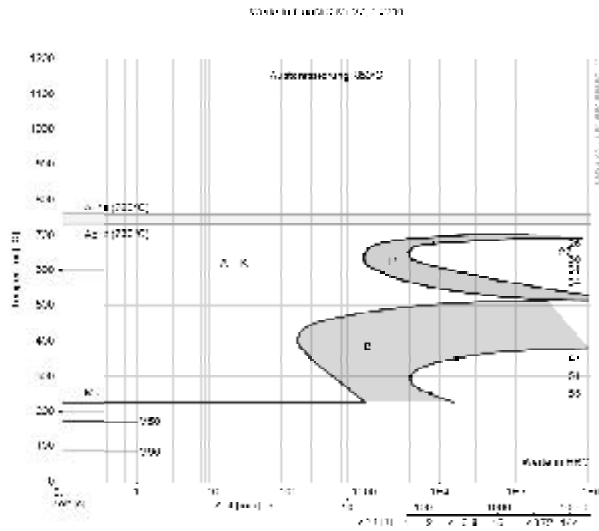

## Hardening and tempering diagram

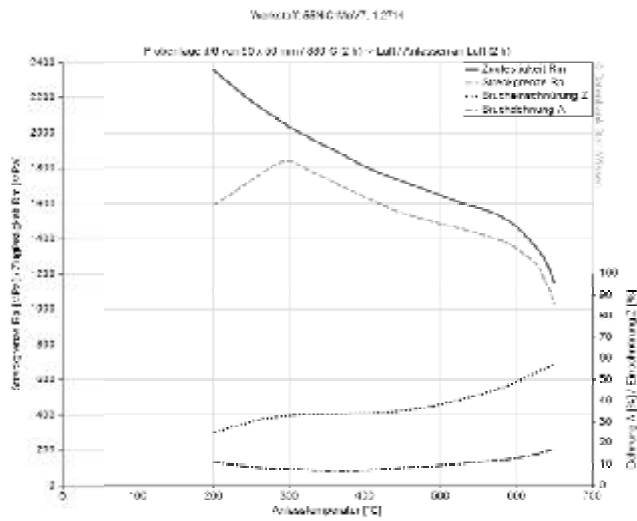

Tempering diagram

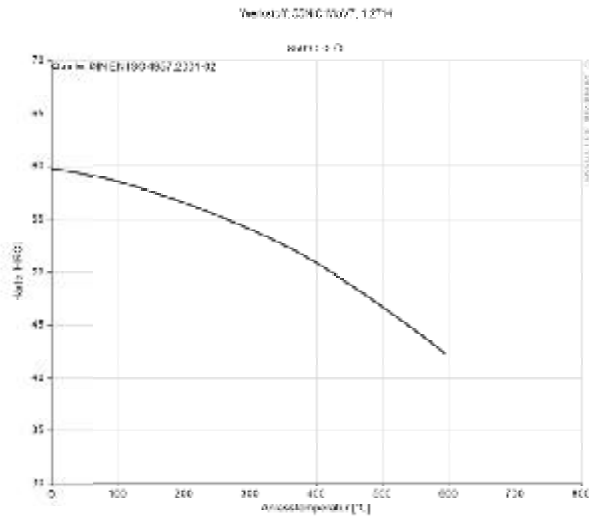

The data shown here is to be used only as an indication of the statistics, thus we accept no liability.  
Diagrams are taken from Datenbank StahlWissen Dr. Sommer Werkstofftechnik  
Issued: 2012

**ABRAMS PREMIUM STEEL**

is a registered trademark of  
Abrams Engineering Services GmbH & Co. KG  
Hannoversche Str. 38 · 49084 Osnabrueck / Germany  
Managing Director: Dipl.-Wi.-Ing. Dr. Juergen Abrams

Amtsgericht Osnabrueck / Germany, HRA 6865  
VAT-No.: DE 221940667  
General Partner: Abrams Engineering Verwaltungs GmbH  
Amtsgericht Osnabrueck / Germany, HRB 20019

T: +49 (0) 5 41/3 57 39-0  
F: +49 (0) 5 41/3 57 39-39

sales@premium-steel.eu  
www.premium-steel.eu  
www.shop.premium-steel.eu  
www.steel-guide.eu

www.premium-steel.eu/news

